
Development of Knowledge-Based Systems for Aluminum Welding

Computer programs offer the extensive knowledge of experienced engineers

BY R. J. NAPOLITANO, H. KULLUK, M. L. NAGURKA, R. P. MARTUKANITZ AND P. B. DICKERSON

Welding engineers experienced with aluminum possess knowledge generally unavailable to others, including those in need of such information such as designers and manufacturers of welded aluminum structures. The experienced engineers are often asked to: 1) recommend appropriate filler metals, 2) recommend starting welding parameters; and 3) diagnose difficulties encountered during aluminum welding. Developing computer-based expert systems in these areas can reduce the time required for others to access the desired information, overcome the limitations associated with the present methods of obtaining this information and provide knowledge transfer by exposing users to the thought processes of experienced welding engineers. Examples of two computer-aided welding systems are described in Refs. 1 and 2.

The present method of determining appropriate filler metals and welding parameters in industry is through the use of selection charts and tables. Although these have served their purpose well, there are advantages to computer methods. With appropriate design, knowledge-based systems can be extended rather easily to contain more information deemed useful to the user. The computer software can provide more complete information that would require literally hundreds of footnotes and additional charts and tables in the present method. For example, the appropriate setting for arc voltage, and consequently amperage, depends on the particular type of filler metal employed in the gas metal arc welding (GMAW) process. The 5XXX series filler metals, with magnesium as the primary alloying element, require higher current and lower arc voltage to

ensure proper metal deposition compared to 4XXX filler metals and maintain total heat input, respectively. Another example is the fact that shielding gas composition as well as flow rate influence weld penetration and cross-sectional area (Refs. 3, 4). The addition of a certain percentage of helium to the argon shielding gas can be advantageous in particular situations. This type of knowledge can readily be incorporated into a knowledge-based system. Another advantage is that it can provide explanations for its conclusions. This exposes users to the thought processes of experienced welding engineers and streamlines knowledge transfer.

Toward this goal, in cooperation with the Aluminum Co. of America (Alcoa), two user-friendly software packages were developed and a third module is in the final prototype stage. One package, the Filler Metal Selector, is a knowledge-based system that recommends optimal filler metals for gas metal arc (GMA) and gas tungsten arc (GTA) welding of aluminum. The second package, the Process Parameter Selector, provides typical starting welding parameters and joint preparations for a variety of base metal thicknesses. Currently under development is a third package, the Weld Defect and Diagnostic System, which is a knowledge-based program to assist in determining causes of weld discontinuities during aluminum welding and to recommend corrective procedures. These three systems constitute the Aluminum Welding Engineer series and represent an integral part of the proposed interactive welding engineering workstation. The software systems were created with the help of several welding engineers, and the systems incorporate their knowledge representing over one hundred years of experience with Alcoa in aluminum welding.

Software Design

After reviewing several expert system shells, it was decided to use Personal Consultant Plus (PC+) marketed by

R. J. NAPOLITANO is with Department of Mechanical Engineering, Carnegie Mellon University. H. KULLUK and M. L. NAGURKA are with Department of Mechanical Engineering and Robotics Institute, Carnegie Mellon University, Pittsburgh, Pa. R. P. MARTUKANITZ is with Applied Research Laboratory, Pennsylvania State University, State College, Pa. P. B. DICKERSON is retired, formerly with Aluminum Co. of America.

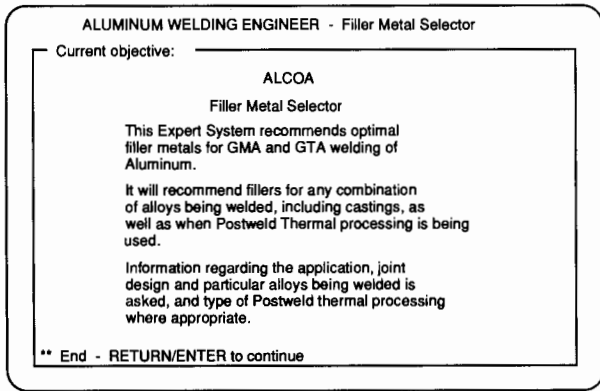


Fig. 1 — Filler metal selector introductory screen.

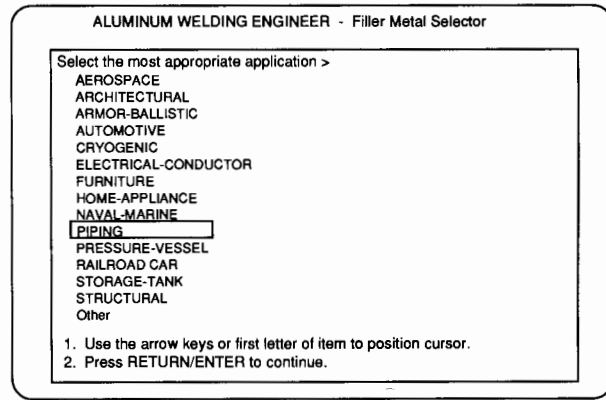


Fig. 2 — List of typical applications in aluminum welding showing the selection of a piping application.

Texas Instruments. The software is inexpensive, can be run on any IBM or fully compatible computer, is well supported and maintained and is easy to learn and use. It provides the ability to access externally written routines and external databases, can be integrated with graphics, and can explain in text why the system reaches a certain conclusion. Additional access to PC Scheme, a dialect of Lisp capable of running on personal computers, is provided, and it was used extensively in the development of these systems.

Personal Consultant Plus is a rule-based expert system shell. The rules themselves are entered into the knowledge base using the Abbreviated Rule Language (ARL). The knowledge-based designer provides translations for each parameter used in the system. PC+ uses these translations and the format of ARL to generate plain-English translations of the rules, useful for development purposes, and for the conclusions that the end user sees. This is an important aspect of the software that allows the users of the system to follow and understand the experts' thought processes represented by the knowledge base. The software has a data type called a frame which allows the knowledge base to be divided into logical segments. This is ex-

tremely useful in the development of large and complex knowledge bases. It also speeds execution times for the end user by loading in only those frames that affect the course of the consultation, i.e., the thought processes represented by the rules. The software is user-friendly, which is exemplified by the presentation of inquiries and conclusions, both graphic and literal, to the end user. This software development tool was used to create the expert systems from the knowledge domains described previously.

Filler Metal Selector

The selection of appropriate filler metals essentially involves optimizing desired weld characteristics under metallurgical and mechanical constraints determined by the materials' chemical and physical properties. The system asks a series of questions related to the above, determines which filler metals are most appropriate for the alloys being welded, evaluates each of these separately and then recommends one or possibly several filler metals. When postweld thermal processing is employed or when welding certain castings and wrought products, there are few filler metals deemed appropriate, and the system simply recom-

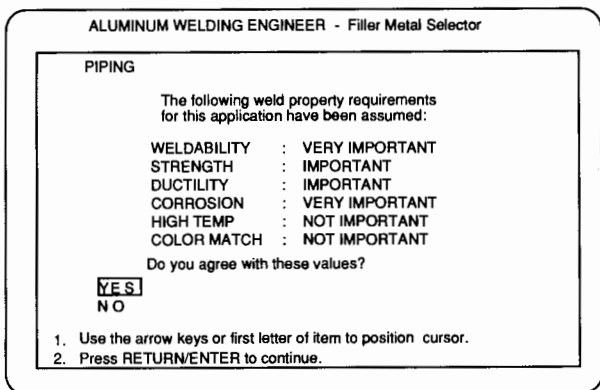


Fig. 3 — Screen showing default weightings of weld properties for a piping application.

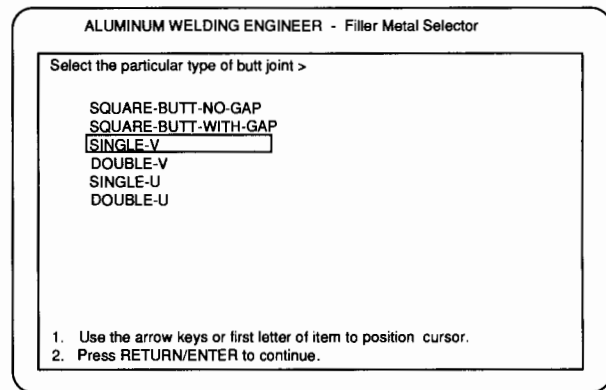


Fig. 4 — Screen for specific type of butt joint with single-V-groove joint design selected.

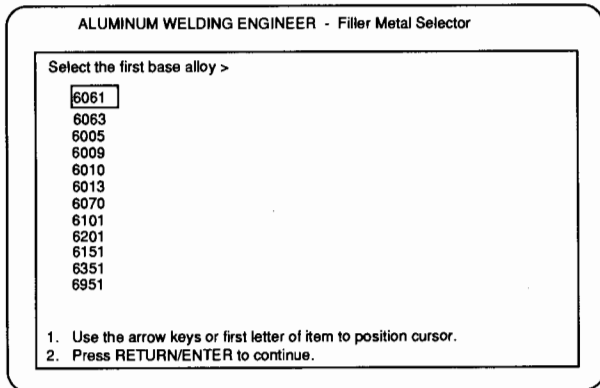


Fig. 5 — Screen for 6XXX series wrought alloys showing 6061 selected.

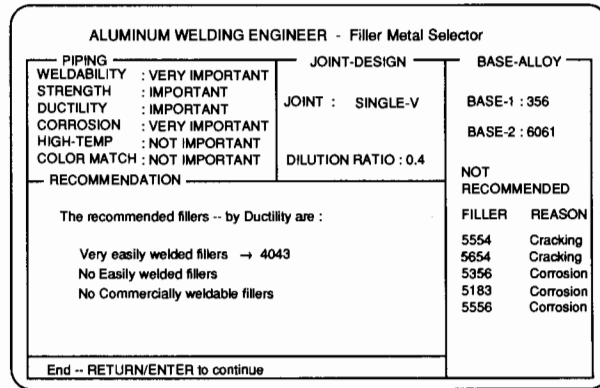


Fig. 6 — Recommendation screen of the filler metal selector for pipe welding 6061 wrought alloy to 356 casting alloy utilizing a single-V-groove joint design.

mends their use.

In general, the following information is required: 1) The application, which dictates desired weld characteristics; 2) the particular joint design; and 3) the base metals being welded. Currently, there is information available for over 60 base metals, including both wrought products and castings.

The system first displays an introductory screen describing the program and its function — Fig. 1. It begins by determining the desired weld characteristics dictated by design requirements and/or service conditions, and then presents the user with a list of possible applications for aluminum welding, such as automotive or aerospace uses, pressure vessels, or home appliances to name a few. This screen is shown in Fig. 2. Once the user selects a particular application, the system retrieves from an external file the default values of the relative importance of six weld properties. The user is shown the default values and may change any or all of the relative weightings. Figure 3 depicts the screen showing relative weightings for a piping application. There are three possible relative weightings that can be assigned to each weld attribute. The weightings (very important, important and not important) determine the order and importance placed on the various weld attributes or characteristics.

The system next asks the user to provide the type of joint that will be welded. For a butt joint, a specific joint design is requested through a screen query, as shown in Fig. 4. A base metal/filler metal dilution ratio is calculated based on the particular joint design and is displayed for confirmation. The default ratio may easily be changed if the user is more confident of a more appropriate dilution ratio.

Information is available for over 60 base metals

The system next asks the user to identify the base materials being welded. The alloy systems that are normally used for the specified application are presented and the system can easily account for welding of dissimilar alloys. Figure 5 shows the screen used for selecting 6XXX series wrought alloys for a piping application.

Once the alloys to be welded are obtained, the system utilizes the dilution ratio to determine applicable filler metals based on the desired joint characteristics. Information pertaining to the applicability of the filler metals is shown by the system, and a final recommendation is made based

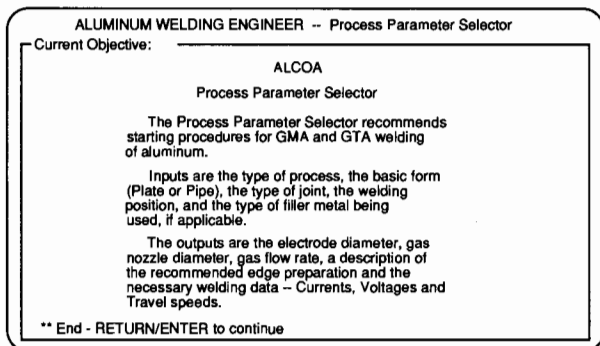


Fig. 7 — Process parameter selector introductory screen.

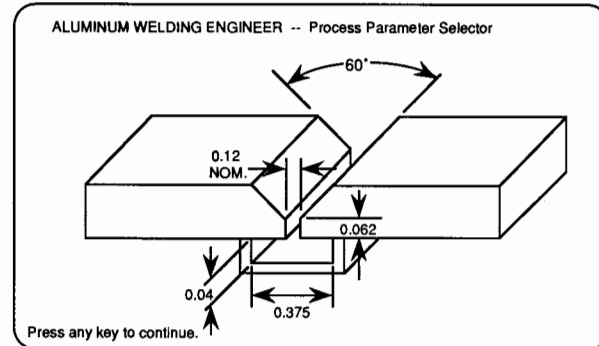


Fig. 8 — Screen output showing recommended single-V-groove joint design for GMA welding a 0.375-in.-thick plate.

ALUMINUM WELDING ENGINEER -- Process Parameter Selector

EQUIPMENT-SPECIFICATION		EDGE-PREPARATION	
PROCESS: GMAW POLARITY: DC(EP) GAS: ARGON CUP DIAMETER: 1/2 in. GAS FLOW: 50 cfm		FORM: PLATE POSITION: FLAT JOINT: BUTT BACKING ROOT OPENING WIDTH: 0.375 in HEIGHT: 0.04 in	
ELECTRODE DIAMETER: 0.062 in.		MIN: 0.125 in.	BEVEL: 60
		MAX: 0.125 in.	LAND: 0.062 in
		NOM: 0.125 in.	
SCHEDULE			
PASS CODE	CURRENT [Amps]	VOLTAGE [Volts]	TRAVEL SPEED [ipm]
1	245	30	21
2	245	30	21
3BR	245	30	21
TOTAL NUMBER OF PASSES: 3			
End -- RETURN/ENTER to continue			

Fig. 9 — Recommendation screen of the process parameter selector detailing suggested gas metal arc welding parameters for 0.375-in.-thick plate welded in the flat position.

on optimizing the desired attributes. Shown in Fig. 6 is the recommendation screen for pipe welding 6061 base metal to a 356 casting alloy utilizing a single-V-groove joint design. The system may also be used to improve the utility of a filler metal by suggesting other joint designs.

Process Parameter Selector

The Process Parameter Selector recommends optimal starting welding parameters for gas metal arc (GMA) and gas tungsten arc (GTA) welding of aluminum. It has over 50 separate databases which contain information about welding parameters, as well as joint designs. It covers both plate and pipe welding and allows for different positions, joint designs and base metal thicknesses.

Over 50 databases contain parameter information

Parameter selection involves collecting information about the particular welding process, the basic form of the base metals, the joint design, the welding position, the base metal thickness and, in certain cases, the type of filler metal employed. The conclusions consist both of the required essential parameters such as current, voltage and travel speed, as well as desired edge preparations.

The general approach the software takes is similar to that of an experienced welding engineer. The program first displays an introductory screen describing the inputs and outputs of the system — Fig. 7. The system first asks which particular process is being used, GMA or GTA welding. It then asks which basic form, plate or pipe, is being used. If pipe is chosen and the process is GMA, the system contains one database that is in the horizontal-rolled position. If pipe is chosen and the process is GTA, the three positions, horizontal-rolled, horizontal-fixed and vertical-fixed may be chosen. If plate is selected, then the system requests what general joint design is of interest. The available joint types are butt, T, lap, corner or edge. The system then asks which welding position is being used, flat, horizontal, overhead or vertical. Also, if GMA welding is chosen, the system needs to know which series filler metal is being used since it affects the choice of welding parameters. The system then retrieves from an appropriate

database the available thicknesses for this particular situation and presents these to the user for selection.

The initial screen output shows the recommended joint design, as shown in Fig. 8, for GMA welding of 0.375-in. (9.5-mm) thick plate. This includes root face thickness, groove angle, root opening width and backing dimensions when necessary. The information provided at this screen is also in literal form on the final screen. The final screen, shown in Fig. 9, summarizes the inputs and provides recommendations.

The approach is similar to that of an experienced welding engineer

The Equipment Specification window and the Edge Preparation window are self-explanatory. The Schedule window provides the actual number of passes and the parameters for each pass. The pass coding utilizes BR to specify backgouging on the root side.

System Verification

Extensive on-site testing has been performed for both the Filler Metal Selector and the Process Parameter Selector. Two issues were of primary concern during this process. The first was reevaluating the experts' conclusions and ensuring the accuracy of their results, while the second issue in verification was to ensure that the system reported these same results to the user along with clear explanations as to how certain conclusions were reached. For the Filler Metal Selector, this involved having the experts recommend filler metals when utilizing less common combinations of aluminum base metals. Their results and reasoning were compared to the system's recommendations. When appropriate, modifications to the system were made to further improve its accuracy. In several cases re-assessment of the experts' recommendations were made. Hundreds of test cases have been performed for this system with excellent corroboration of the experts' recommendations. For the Process Parameter Selector, informa-

Hundreds of test cases have been performed

tion was taken from handbooks that are well maintained and represent values considered optimal by welders with many years of experience in aluminum welding. In this case, several conditions were tested at random by producing weldments using the system's recommendations for welding parameters and joint design. With minor modifications to the parameters, the system functioned as expected and provided excellent starting conditions.

Conclusions

The development of the Filler Metal Selector and the Process Parameter Selector as well as initial work in constructing the Weld Defect and Diagnostic System have led to the following conclusions:

1) The application of knowledge-based systems for welding is an effective vehicle for capturing experts' knowledge and transferring it to others. With proper design, such systems allow easy access to the knowledge and thought processes of experienced aluminum welding engineers.

2) The systems significantly reduce the time required to obtain the desired information.

3) Knowledge-based systems can outperform current methods for obtaining desired information.

4) Knowledge-based systems can be used successfully by a wide variety of end users in terms of their degree of experience in aluminum welding.

Acknowledgments

The authors would like to thank Alcoa, and the Ben Franklin Partnership Program of Pennsylvania for funding this work.

References

1. Kuhne, A. H., Gary, H. B., and Prinz, F. B., 1987. An expert system for robotic arc welding. *Welding Journal* 66(11):21-25.

2. Lucas, W. 1987. Microcomputer systems, software and expert systems for welding engineering. *Welding Journal* 66(4):27-30.

3. Reichelt, W. R., Evancho, J. W., and Hoy, M. G. 1980. Effects of shielding gas on gas metal arc welding aluminum. *Welding Journal* 59(5):147-s to 155-s.

4. Brungraber, R. J., and Nelson, F. G. 1973. Effect of welding variables on aluminum alloy weldments. *Welding Journal* 52(3):97-s to 113-s.

Stop Flash in its Tracks

Koike Sentinel flashback arrestors add safety to your cutting operation by reducing flashback danger. Very compact in size, they disperse flash and absorb heat just like much larger arrestors. The easy-to-reset Sentinel Plus connects to your regulator, while the Super Sentinel attaches to hand and machine torches. For fuel gas and oxygen. See your Koike Aronson distributor or write for free data sheet.

NOTE: In the event of flashback, carefully inspect arrestor, couplings and all connected equipment prior to reuse.



KOIKE ARONSON

635 W. Main St.
Arcade, NY 14009
(716) 492-2400

Circle No. 18 on Reader Info-Card

50% Off Hotel Rates At Over 1,500 Locations Nationwide

**"American Welding Society" Partnership With Quest International
Gives You Preferred Access To The Nation's Leading Hotel Savings Program**

Imagine it! You'll select from over 1,500 terrific hotels, all available at 50% savings!

How? With Quest International. And you can join Quest right now at huge savings.

You've Got The Advantage

A Quest membership retails for \$99. But through a special agreement with Destinations, Inc., (group distributors for Quest), you'll get in at a fraction of the retail cost! **Just \$29.95!**

50% Off! Are They Crazy?

Why do hotels do it? -- Simple. -- Profits. On average, annual hotel occupancy levels are around 65 percent. But remember that 65% occupancy means 35 of every 100 rooms sit empty each night. And any additional rooms sold means added profit for the hotel. *Even when you stay for half-price!*

Occasionally a hotel fills completely, like during a convention. If they expect to fill they may decline a half-price reservation. But, the rest of the time they'd love to have you stay!

Makes sense, doesn't it?

The hotel earns income it wouldn't have otherwise made, and you save a full 50%.

The bottom line is this. Quest members find space is available the vast majority of the time. And you save a full 50%! At your special \$29.95 Quest rate, you're likely to save more than that the very first time you use it!

How Do I Know Where I Can Stay?

Participating Quest hotels include Holiday Inns, Hiltons, Best Westerns, Sheratons and more! Virtually every major chain there is! And you get your own 80-page hotel directory. Plus, every 90 days you'll receive a new hotel directory at no extra charge.

Your one-year directory subscription is absolutely free. Other Quest members pay \$6.00 extra for this convenient feature. But through this special offer, you get them FREE!

Try Quest All Year -- Risk Free!

Take Quest on the family vacation. Or a weekend getaway. Try Quest all year. If you're not fully satisfied you get all your money back at any time during the life of your membership. A toll-free phone call is all it takes to cancel and get a full refund. No questions asked.

Call 1-800-STAY-4-50 and join Quest now!

CALL 1-800-STAY-4-50 and use your Visa, MasterCard or American Express

Yes! I Want To Join Quest International & Save 50% On My Hotel Bills!

Enclosed is my check or money order for \$29.95, made payable to "Destinations, Inc." (Total: \$36.95 with a spouse card - Please check box below)

Charge my: Visa MasterCard American Express

Account Number _____ Exp. Date: _____

Yes! Send a personalized Quest Card for my spouse. Add \$7.00 -- Total: \$36.95

Spouse Name _____

Name _____ Signature _____

Address _____

City _____ State _____ Zip Code _____

Call 1-800-782-9450 -- Or, mail to: AWS Quest Offer, One Lake Aspen Park,

Access # 1875-12 P.O. Box 22800, Yakima, WA 98907-2800
Allow 2 - 3 weeks for delivery -- UPS or Fed Ex available at a nominal fee